

A Precise Measurement of the Oxygen Isotope Effect on the Néel temperature in Cuprates

E. Amit* and A. Keren

Physics Department, Technion, Israel Institute of Technology, Haifa 32000, Israel.

J. S. Lord and P. King

Rutherford Appleton Laboratory, Chilton Didcot, Oxfordshire OX11 0QX, U.K.

A limiting factor in the ability to interpret isotope effect measurements in cuprates is the absence of sufficiently accurate data for the whole phase diagram; there is precise data for T_c , but not for the antiferromagnetic transition temperature T_N . Extreme sensitivity of T_N to small changes in the amount of oxygen in the sample is the major problem. This problem is solved here by using the novel compound $(\text{Ca}_{0.1}\text{La}_{0.9})(\text{Ba}_{1.65}\text{La}_{0.35})\text{Cu}_3\text{O}_y$ for which there is a region where T_N is independent of oxygen doping. Meticulous measurements of T_N for samples with ^{16}O and ^{18}O find the absence of an oxygen isotope effect on T_N with unprecedented accuracy. A possible interpretation of our finding and existing data is that isotope substitution affects the normal state charge carrier density.

Isotope substitution is a powerful experimental tool used to investigate complex systems. Ideally, the isotope substitution affects only one parameter, for example, a phonon frequency which is directly related to the nuclear mass. However, the strong coupling of many parameters in cuprates highly limit the ability to interpret isotope effect (IE) experiments. Eventhough the oxygen isotope substitution is known to affect the superconductivity transition temperatures T_c , it is unclear whether it primarily impacts phonons, polarons, magnons, doping or other physical properties.[1]

The isotope effect is usually described using the isotope coefficient α via the relation

$$T_q \propto M^{-\alpha_q} \quad (1)$$

where T_q is a phase transition temperature, M is the isotope mass and $q = C, N$, and g for the superconducting (SC), antiferromagnetic (AFM) and spin glass critical temperatures, respectively. In many conventional superconductors α was found to be very close to 0.5.[2, 3] The explanation of this α in terms of Cooper pairs glued by phonons was one of the triumphs of the BCS theory for metallic superconductors.[4]

In cuprates the isotope effect is much more complicated and α is not single valued and varies across the phase diagram. The consensus today for YBCO like compounds is that in the SC phase, close to optimal doping, the oxygen IE is

$$\alpha_C^{od} = 0.018 \pm 0.005, \quad (2)$$

which is very small but non zero.[5] On the SC dome α_C increases as the doping decreases.[6, 7] In the glassy state less data is available, but it seems that the isotope effect reverses sign and α_g becomes negative. In extremely underdoped samples, where long range AFM order prevails at low temperatures, data is scarce, controversial,

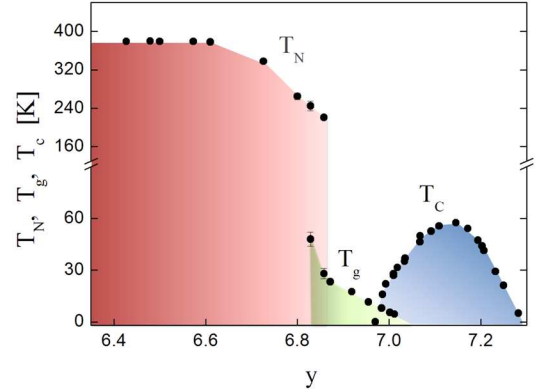


FIG. 1. The $(\text{Ca}_{0.1}\text{La}_{0.9})(\text{Ba}_{1.65}\text{La}_{0.35})\text{Cu}_3\text{O}_y$ phase diagram [15]. The antiferromagnetic, spin glass, and superconducting phases are represented in red, green and blue, respectively. For $y < 6.6$ the Néel temperature does not depend on y . This enables accurate measurements of the oxygen isotope effect on the Néel temperature T_N .

and has relatively large error bars.[5, 8] The most recent measurements with $\text{Y}_y\text{Pr}_{1-y}\text{Ba}_2\text{Cu}_3\text{O}_{7-\delta}$ show that $\alpha_N = 0.02(3)$ in the parent compound.[5] There are also several theories dealing with the variation of α along the phase diagram,[9–14] but since α_C^{od} and α_N are within an error bar of each other one cannot contrast these theories with experiments. In particular, it is impossible to tell whether the same glue that holds the spins together holds the cooper pair together, or not. Increasing the accuracy of the IE measurements of the Néel temperature will shed light on the role of isotope substitution.

As mentioned above, a major limitation on the measurements of α_N is the strong dependence of T_N on doping. For example, in $\text{Y}_y\text{Pr}_{1-y}\text{Ba}_2\text{Cu}_3\text{O}_{7-\delta}$, T_N decreases with increasing doping at a rate $\Delta T_N = 2.5$ K per $\Delta y = 0.01$. This strong temperature dependence is, of course, common to many other cuprates. As a conse-

* Electronic address: eranamita@gmail.com

quence, it is very difficult to prepare two samples with exactly the same T_N even with the same isotope. The smallest fluctuation in either y or δ may lead to a huge fluctuation in T_N regardless of the isotope effect. This is not the case for the $(\text{Ca}_{0.1}\text{La}_{0.9})(\text{Ba}_{1.65}\text{La}_{0.35})\text{Cu}_3\text{O}_y$ where T_N is constant for oxygen density $y < 6.6$, as can be seen in Fig. 1.[15]

For our experiments, four sintered pellets were prepared using standard techniques.[16] Two of the pellets were enriched with ^{18}O isotope and two with ^{16}O isotope in the same procedure: The samples were placed simultaneously in two closed tubes, each with different isotope gas, and then they were heated to allow the isotope to diffuse into the sample. In order to achieve a higher percentage of gas, the enrichment was repeated several times.

The ^{18}O isotope content in the samples was determined based on measurements of gas composition being in equilibrium with the sample during the exchange. Balzers Prisma mass spectrometer was used to analyze in situ isotopic composition of the atmosphere. After the exchange process was performed, the weight increase of the sample was also determined as the light ^{16}O isotope was exchanged with the heavy ^{18}O . The isotope enrichment in the samples measured by both methods looked to be higher than 80%. Finally a Thermal Analysis experiment (TA) was performed for the investigated samples after all experiments described in this work were fulfilled in order to verify the isotope enrichment. The samples were heated up to 1200°C in the NETSCH STA 449C Jupiter analyzer in a stream of helium. During the TA experiments, ion current signals for the $^{18}\text{O}_2$, $^{18}\text{O}^{16}\text{O}$ and $^{16}\text{O}_2$ molecules were measured using a mass spectrometer (ThermoStar Pfeiffer Vacuum). The results are shown on Fig. 2. The isotope content deduced from these measurements (comparing peak areas for the signals of particular oxygen molecules) was larger than 70%.

The oxygen IE was measured using zero-field muon spin rotation/relaxation (μSR). We particularly used the ISIS facility, which allows low muon relaxation rate and rotation frequency measurements. This is ideal for measurements near magnetic phase transitions where the muon signal varies on a long time scale. μSR data at temperatures close to the phase transition are shown in Fig. 3. As the temperature is lowered from 383.4 K the relaxation rate increases. At $T = 378.5$ K oscillations appear in the data indicating the presence of long range magnetic order. The frequency of oscillations and the relaxation rate increase as the temperature is further lowered. The formula

$$P_z(t) = P_m(ae^{-\lambda_1 t} + (1-a)e^{-\lambda_2 t} \cos(\omega t)) + P_n e^{-\Delta t} \quad (3)$$

was fitted to the muon polarization, where P_m , λ_1 , λ_2 and ω are the polarization, relaxation rates, and frequency of muons spin in the fraction of the samples which is magnetic, and a is the weighting factor between the muons experiencing transverse field and longitudinal field. This factor is close to 2/3 and temperature-independent. P_n

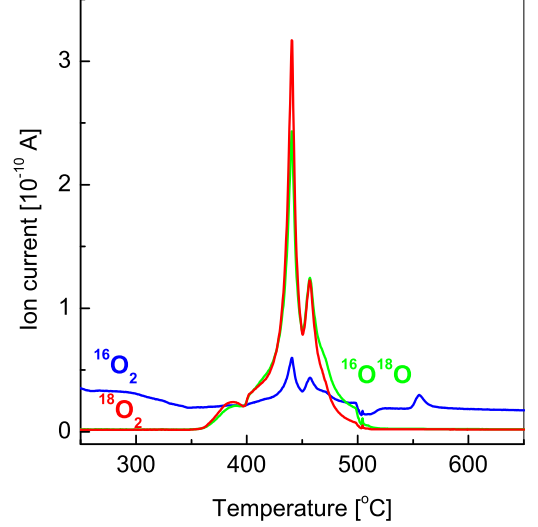


FIG. 2. Ion current signals for the $^{18}\text{O}_2$, $^{18}\text{O}^{16}\text{O}$ and $^{16}\text{O}_2$ molecules (red, green and blue color, respectively) obtained during heating of the sample in a stream of helium. This graph shows that the ^{18}O isotope fraction in the samples is bigger than 70% (see text).

and Δ are the polarization and relaxation of the spin of muons that stopped in the non-magnetic volume of the sample. The solid lines in Fig. 3(a) represent the fits.

The AFM order parameter is determined by the frequency $\omega = \gamma B$, where B is the average magnetic field at muon site and γ is the muon gyromagnetic ratio. This frequency can be easily extracted from the μSR data well below the transition but is very difficult to determined near the transition. A second approach is to treat the magnetic volume fraction P_m as the order parameter.[5, 18] P_m can be followed more closely to T_N , although this parameter also has large error bars when ω is not well defined. We used an alternative approach similar to Ref. [19]; we define an order parameter which, does not require a fit, via the relation

$$\mathcal{OP}(T) \equiv \frac{\langle P_{inf} \rangle - \langle P(T) \rangle}{\langle P_{inf} \rangle - \langle P(0) \rangle} \quad (4)$$

where $\langle P(T) \rangle$ is the average polarization at temperature T , and $\langle P_{inf} \rangle$ is the average polarization above the transition. The denominator normalizes $\mathcal{OP}$ to 1 at zero temperature. All three order parameters for one sample are shown in Fig. 3(b). The transition temperatures determined using the different order parameters are in good agreement. The advantages of $\mathcal{OP}$ are clear: it is a model free and has very small uncertainties.

In Fig. 4 we present the $\mathcal{OP}$ for two samples with ^{16}O and one with ^{18}O around 380 K. A wide temperature range from 50 to 410 K is shown in the inset for an ex-

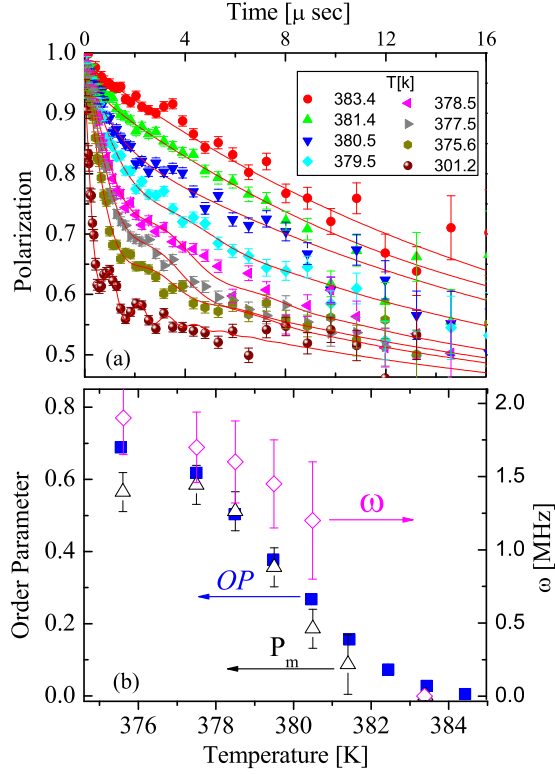


FIG. 3. (a) The μ SR raw data at different temperatures and fits of Eq. 3 to the data in solid lines. (b) Comparison between three different methods used to describe the AFM phase transition: (I) the muon precession frequency ω obtained from Eq. 3, (II) the magnetic volume fraction P_m determined by Eq. 3, and (III) $\mathcal{OP}$ calculated by Eq. 4.

periment done on separate occasion, in which two samples of ^{18}O and one with ^{16}O were examined. We determine T_N by fitting a straight line to the data in the main panel of Fig. 4 in the temperature range 378 to 382 K, for each sample, and taking the crossing with the temperature axis. We find that $T_N^{18} = 382.49(0.34)$ K and $T_N^{16} = 382.64(0.29)$ K. For 100% isotope substitution the isotope exponent is determined by

$$\alpha_N = -\frac{M_o^{16}}{T_N^{16}} \frac{T_N^{18} - T_N^{16}}{M_o^{18} - M_o^{16}}. \quad (5)$$

When taking into account the isotopic fraction in the samples we obtain:

$$\alpha_N = 0.005 \pm 0.011. \quad (6)$$

This result indicates that $\alpha_N < \alpha_C^{od}$ (see Eq. 2) beyond the error bars, and is consistent with no isotope effect on T_N .

One possible interpretation of these results is that magnetic excitations are not relevant for superconductivity

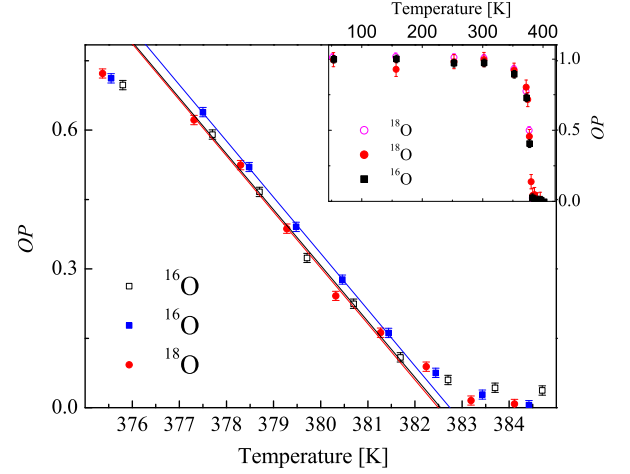


FIG. 4. The parameter $\mathcal{OP}$ (see Eq. 4) versus temperature near T_N for ^{18}O and ^{16}O rich samples. The solid lines are fits to the data near the phase transition used to determine T_N . The inset shows a second experiment on the entire temperature range. No oxygen isotope effect of T_N is observed within experimental error.

since the isotopes affect T_c without affecting T_N . This approach was presented, for example, by Zhao *et al.*[9] They found that samples enriched with ^{18}O have longer penetration depth λ than samples enriched with ^{16}O with the same amount of oxygen per unit cell. λ is related to the SC carrier density n_s and effective mass m^* by $\lambda^{-2} \propto n_s/m^*$ so a priori both n_s and m^* can be affected by isotope substitution.[17] They ruled out the possibility that the number of carriers concentration varies by demonstrating that the thermal expansion coefficient of samples with different isotopes are the same. The authors therefore concluded that the IE changes the mass of the cooper pairs, which could be explained by polaronic supercarriers.

An alternative interpretation is that the isotopes affect the efficiency of doping, as suggested in Ref. [13]. To demonstrate this interpretation we present in Fig. 5(a) the critical temperatures in $\text{Y}_y\text{Pr}_{1-y}\text{Ba}_2\text{Cu}_3\text{O}_{7-\delta}$ for the two different isotopes taken from Ref. [5]. T_N^{18} seems to be a bit higher than T_N^{16} , but T_c^{18} is a bit lower than T_c^{16} . However, if we define an efficiency parameter K_i which relates the number of holes p to the number of oxygens in the unit cell y via $p = K_i y$, where i stands for the isotope type, we can generate a unified phase diagram. This is demonstrated in Fig. 5(b) and 5(c) for T_N and T_c , respectively. In these graphs three different values of K_{18} are used to generate p while keeping $K_{16} = 1$. When using $K_{18} = 0.98$, both curves of T_N and T_c versus p for the two different isotopes collapse to the same curve. Similar scaling of the doping axis was applied to the $(\text{Ca}_x\text{La}_{1-x})(\text{Ba}_{1.75-x}\text{La}_{0.25+x})\text{Cu}_3\text{O}_y$ system [15] and was explained by NQR.[20]

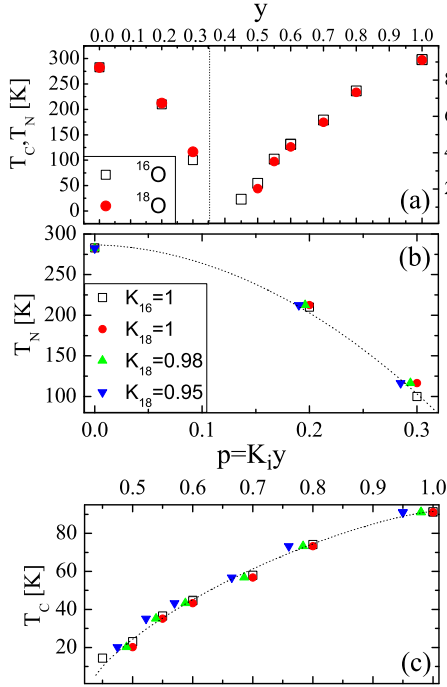


FIG. 5. (a): Oxygen isotope effect of T_N (left) and T_c (right) in $\text{Y}_y\text{Pr}_{1-y}\text{Ba}_2\text{Cu}_3\text{O}_{7-\delta}$ taken from Ref. 5. The ^{18}O and ^{16}O samples are in filled red circles and empty black squares, respectively. Figure (b) and (c) are demonstration of the IE using charge carriers density $p = K_i y$, instead of oxygen content y . The values of K_i are given in the the figures. Green triangles ($K_i = 0.98$) represent reduction of 2% in the number of charge carriers in the ^{18}O samples compared to the ^{16}O sample. In this case both T_N and T_c are functions of p regardless of the isotope.

Next we discuss the IE on the stiffness in the above scenario. We assume that the effective mass of the SC charge carrier m^* , the critical p where superconductivity starts p_{crit} , and where T_c is optimal p_{opt} , are not affected by the isotope substitution as suggested by Fig. 5(c) and demonstrated in Ref. [20]. The stiffness can be measured by the muon transverse relaxation rate σ , and it is expected that:[17]

$$\sigma^i = C(p^i - p_{crit}) \quad (7)$$

where C is a constant. Dividing the differential of σ from Eq. 7 by the relaxation at optimal doping yields:

$$\frac{d\sigma}{\sigma_{opt}} = \frac{dp}{p_{opt} - p_{crit}} = \frac{y(K_{16} - K_{18})}{p_{opt} - p_{crit}} \quad (8)$$

The expected change in the stiffness due to isotope substitution can be calculated from Eq. 8 using $p_{opt} = 1$, $p_{crit} = 0.42$ (which are extracted from Fig. 5(b)) and $\sigma_{opt} = 3.0 \mu\text{s}^{-1}$. [21] For $y = 0.8$, $K_{16} = 1$ and $K_{18} = 0.98$ we get $d\sigma = 0.083 \mu\text{s}^{-1}$. This value is consistent with the experimental value of $d\sigma = 0.08(1) \mu\text{s}^{-1}$ reported in Ref. [21]. In other words a 2% difference in the doping efficiency between the two isotopes can explain both the variations in phase diagram in Fig. 5(a) and the variation in the stiffness.

Our experiment shows that oxygen isotope substitution does not affect the Néel temperature and therefore does not play a role in magnetic excitations. However, the isotope effect of T_c does not necessarily imply that phonons play a role in cuprate superconductivity. We show that an isotope dependent doping efficiency can explain the variation in T_c and in the magnetic penetration depth between samples rich in ^{16}O or ^{18}O . We would like to thank the ISIS pulsed muon facility at Rutherford Appleton Laboratory, UK for excellent muon beam conditions. This work was funded by the Israeli Science Foundation and the Posnansky research fund in high temperature superconductivity.

-
- [1] P. A. Lee, Rep. Prog. Phys. **71**, 012501 (2008).
 - [2] E. Maxwell, Phys. Rev. **78**, 477 (1950).
 - [3] C. A. Reynolds, B. Serin, W. H. Wright, and L. B. Nesbitt, Phys. Rev. **78**, 487 (1950).
 - [4] J. Bardeen, L. N. Cooper, and J. R. Schrieffer, Phys. Rev. **108**, 1175 (1957).
 - [5] R. Khasanov *et al.*, Phys. Rev. Lett. **101**, 077001 (2008).
 - [6] D. J. Pringle, G. V. M. Williams, and J. L. Tallon, Phys. Rev. B **62**, 12527 (2000).
 - [7] H. Keller, Springer-Verlag Berlin Heidelberg 2005.
 - [8] G. Zhao, K. K. Singh and D. E. Morris, Phys. Rev. B **50**, 4112 (1994).
 - [9] G. Zhao, M. B. Hunt, H. Keller and K. A. Müller, Nature **385**, 236 (1997).
 - [10] A. Bill, V. Z. Kresin, and S.A. Wolf, cond-mat/9801222
 - [11] J. F. Baugher *et al.*, The Journal of Chemical Physics **50**, 4914 (1969)
 - [12] D. S. Fisher *et al.*, Phys. Rev. Lett **61**, 482 (1988).
 - [13] V. Z. Kresin and S. A. Wolf, Phys. Rev. B **49**, 3652(R) (1994).
 - [14] M. Serbyn and P. A. Lee, cond-mat/1009.2429.
 - [15] R. Ofer *et al.*, Phys. Rev. B **74**, 220508(R) (2006).
 - [16] D. Goldschmidt *et al.*, Phys. Rev. B **48**, 532 (1993).
 - [17] Y. J. Uemura *et al.*, Phys. Rev. Lett. **62**, 2317 (1989).
 - [18] R. Ofer, A. Keren, O. Chmaissem and A. Amato, Phys. Rev. B **78**, 140508(R) (2008).
 - [19] M. Shay *et al.*, Phys. Rev. B **80**, 144511 (2009).
 - [20] E. Amit and A. Keren, Phys. Rev. B **80**, 144511 (2010).
 - [21] R. Khasanov *et al.*, Phys. Rev. B **74**, 064504 (2004).